

UNDERSTANDING THE LACK OF FULLERENES IN FULLERENE-LIKE CARBONS

Jacob W. Martin,^{1,2}* Leonard Nyadong,³ Caterina Ducati,⁴ Merilyn Manley-Harris,⁵ Alan G. Marshall,⁶ and Markus Kraft^{1,2,7}

¹*Department of Chemical Engineering and Biotechnology, University of Cambridge, West Site, Philippa Fawcett Drive, Cambridge, CB3 0AS, United Kingdom.* ²*Cambridge Centre for Advanced Research and Education in Singapore (CARES), Singapore, 138602.* ³*Phillips 66 Research Center, OK 74003-6607, United States.* ⁴*Department of Materials Science and Metallurgy, University of Cambridge, United Kingdom.* ⁵*School of Science, University of Waikato, New Zealand.* ⁶*National High Magnetic Field Laboratory, Florida State University, FL 32310-4005, United States.* ⁷*School of Chemical and Biomedical Engineering, Nanyang Technological University, Singapore 637459*

*Presenting author's e-mail: jwm50@cam.ac.uk

Introduction

Significant evidence has been demonstrated for fullerene-like curved carbon networks in non-graphitising carbons such as polygonalised structures [1] and non-hexagonal rings [2]. However, many mass spectrometry studies of charcoals have found a lack of fullerenes, such as C₆₀ and C₇₀ [3]. One of the ions of interest is the mass-to-charge (m/z) 701 ion, near the m/z of C₆₀, which has been found in glassy carbon and in many charcoal samples [3]. We have previously interpreted this ion as belonging to a planar graphitic fragment and developed a microcrystalline model of charcoal [3]. Recently, we explored the thermal annealing of fullerenes in arc carbon into a polymerised structure with evidence for giant fullerenes and found the magic number fullerenes were consumed and oxygen integrated into the nanostructure of fullerene arc-carbon [4].

In this work, making use of a range of highly sensitive and accurate mass spectrometers we have explored the nanostructure of gasification charcoal. We compare the results with heat treated fullerene arc-carbon finding a similar nanostructure supported by Raman spectroscopy and electron microscopy.

Methods

We made use of a laser desorption ionisation time-of-flight, Fourier transform ion cyclotron resonance and electrospray ionisation time-of-flight-mass spectrometers. An FEI Tecnai F20 electron microscope was used at an accelerating voltage of 200 kV. Raman spectra were collected on a Horiba LabRAM HR spectrometer. Reactive molecular dynamics making use of the REBO-II reactive forcefield were used to explore the surface reconstruction and topology of this network.

Results and Discussion

We were unable to detect any magic number fullerenes C₆₀ or C₇₀ in the gasification charcoal samples using LDI-TOF MS or the highly sensitive FT-ICR MS method. The m/z 701 ion, near the m/z of C₆₀, was found to be a breakdown product of pyrolysis and not a persistent part of the nanostructure. When ablating the charcoal using a high laser power (12.8 mJ/cm²) oxygenated ions were generated, separated by m/z 24, suggesting cage-like oxygenated carbon fragments. Similar

distributions of oxygenated ions were found for the thermally annealed arc-carbon suggesting a shared nanostructure (**Figure 1**). This indicates that small magic number fullerenes are not stable in solid state thermal annealing and polymerise along with intercalating oxygen. This suggests that an annealed fullerene-like nanostructure would not be expected to contain small unstable magic number fullerenes.

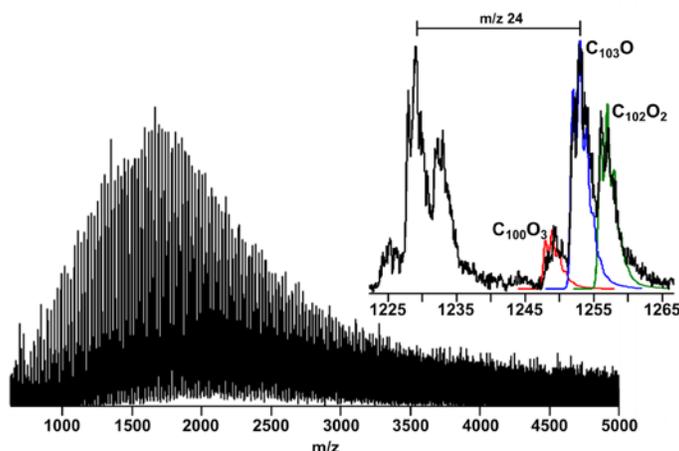


Figure 1. LDI-TOF mass spectrum of charcoal with inset showing the peak structure.

High resolution transmission electron microscopy (HRTEM) showed highly curved nanostructures. *Onion-like* structures were also observed. Layered regions were also observed alongside the curved features. Raman spectroscopy showed significant intensity between the D and G bands which has recently been computationally found to arise from the pentagonal ring breathing mode which is upshifted from the hexagonal breathing mode D band. A carbon surface was reconstructed using reactive molecular dynamics. The curvature is found to be integrated from non-hexagonal rings as well as non- sp^2 defects which close the surface of the solid providing a surface of low reactivity. Simulated HRTEM images reveal curved and layered fringes, leading us to suggest (along with the experimental results) a *stacked, fulleroid-like nanostructure* for this material.

Conclusions

No magic number fullerenes were found in a gasification charcoal but larger oxygenated fragments were found and were also found in thermally annealed arc-carbon. These results, along with HRTEM and Raman spectroscopy, support a *stacked, fulleroid-like nanostructure*.

Acknowledgment

The authors acknowledge financial support from the National Research Foundation (NRF), Prime Minister's Office, Singapore, under its Campus for Research Excellence and Technological Enterprise as well as the U.S.A National Science Foundation Division of Materials Research through DMR-11-57490h.

References

1. PJF Harris et al., *Philos. Mag. A*, **1997**, 76, 667, 2. PJF Harris et al., *J. of Phys.* **2010**, 241, 012050
3. Bourke et al., *Indus. & Eng. Chem. Res.*, **2007**, 46, 5954, 4. JW Martin et al., *Carbon*, **2017**, 125, 132
5. JW Martin et al., *Environ. Sci. Technol.*, **2019**, 53, 3538